

Electron-phonon interaction in cuprate-oxide superconductors

Fusayoshi J. Ohkawa

*Division of Physics, Graduate School of Science, Hokkaido University, Sapporo 060-0810, Japan**
(Received ?? December 2003)

We propose a novel electron-phonon interaction arising from the modulation of the superexchange interaction by phonons. It is enhanced by spin and superconducting fluctuations, which are developed mainly because of the superexchange interaction. It must be responsible for the softening of phonons and kinks in the dispersion relation of quasi-particles. However, the superexchange interaction must be mainly responsible for the formation of Cooper pairs.

PACS numbers: 74.20.-z, 71.38.-k, 75.30.Et

It is an important issue to elucidate the mechanism of high- T_c superconductivity occurring on CuO_2 planes [1]. Two observations, the softening of phonons [2, 3, 4, 5, 6] and kinks in the quasi-particle dispersion [7, 8, 9, 10], imply the relevance of the electron-phonon interaction. One may argue that it must be responsible for high- T_c superconductivity [8]. Its origin and role should be clarified.

Doped *holes* mainly go into O ions. This implies that the charge susceptibility of $3d$ electrons on Cu ions is much smaller than that of $2p$ electrons on O ions and charge fluctuation of $3d$ electrons can never be developed. Then, the conventional electron-phonon interaction, which directly couples with charge fluctuations, can play no crucial role. On the other hand, antiferromagnetic spin (AFS) and superconducting (SC) fluctuations are certainly developed. One may argue that their developments are because of the superexchange interaction. It is shown in early papers [11, 12] that the condensation of $d\gamma$ -wave Cooper pairs bound by the superexchange interaction can explain observed T_c . It is shown in a previous paper [13] that pseudo-gaps appear because of large life-time widths of quasi-particles due to SC fluctuations. Suggested by these arguments, we propose in this Letter an electron-phonon interaction arising from the modulation of the superexchange interaction by phonons.

It is shown in another previous paper [14] that Gutzwiller's quasi-particle band [15] lies between the lower and upper Hubbard bands [16] in metallic phases in the vicinity of the Mott-Hubbard transition. The superexchange interaction arises from the virtual exchange of pair excitations of electrons in spin channels across the lower and upper Hubbard bands; as long as the Hubbard splitting is significant, it works between Gutzwiller's quasi-particles or their renormalized ones [17]. When nonzero bandwidths of the lower and upper Hubbard bands are ignored, the exchange constant between nearest-neighbor Cu ions is given by

$$J = -\frac{4V^4}{(\epsilon_d + U - \epsilon_p)^2} \left[\frac{1}{\epsilon_d + U - \epsilon_p} + \frac{1}{U} \right], \quad (1)$$

with V the transfer integral between $3d$ and $2p$ orbitals on adjacent Cu and O ions, and ϵ_d and ϵ_p their energy

levels. The exchange constant depends on V , ϵ_p and ϵ_d 's of adjacent Cu ions in such a way that

$$\Delta J = \frac{V^4}{(\epsilon_d + U - \epsilon_p)^3} \left[\frac{6}{\epsilon_d + U - \epsilon_p} + \frac{4}{U} \right] \times (\Delta\epsilon_{di} + \Delta\epsilon_{dj} - 2\Delta\epsilon_{p[ij]}) + 2\frac{J}{V}(\Delta V_{i,[ij]} + \Delta V_{j,[ij]}), \quad (2)$$

with $\Delta\epsilon_{di}$ a variation of ϵ_d of the i th Cu ion, $\Delta\epsilon_{p[ij]}$ a variation of ϵ_p of the $[ij]$ th O ion that lies between the i th and j th Cu ions, and $\Delta V_{i,[ij]}$ that of V between the i th Cu ion and the $[ij]$ th O ion. When we take the x - and y -axes along Cu-O-Cu bonds, they are given by

$$\Delta\epsilon_{di} = A_d [\mathbf{e}_x \cdot (\mathbf{u}_{i,x+} - \mathbf{u}_{i,x-}) + \mathbf{e}_y \cdot (\mathbf{u}_{i,y+} - \mathbf{u}_{i,y-})], \quad (3a)$$

$$\Delta\epsilon_{p[ij]} = A_p [\mathbf{e}_{ij} \cdot (\mathbf{u}_i - \mathbf{u}_j)], \quad (3b)$$

$$\Delta V_{i,[ij]} + \Delta V_{j,[ij]} = A_V [\mathbf{e}_{ij} \cdot (\mathbf{u}_i - \mathbf{u}_j)], \quad (3c)$$

with A_d , A_p and A_V being constants, $\mathbf{u}_i$ the displacement of the i th Cu ion, $\mathbf{u}_{i,\xi_s}$ that of an O ion on the adjacent $s = +$ or $s = -$ side along the ξ -axis of the i th Cu ion, $\mathbf{e}_x = (1, 0)$, $\mathbf{e}_y = (0, 1)$, and $\mathbf{e}_{ij} = (\mathbf{R}_i - \mathbf{R}_j)/|\mathbf{R}_i - \mathbf{R}_j|$, with $\mathbf{R}_i$ the position of the i th Cu ion. Displacements of the i th Cu and the $[ij]$ th O ions are given by

$$\mathbf{u}_i = \sum_{\lambda\mathbf{q}} \frac{\hbar v_{d,\lambda\mathbf{q}}}{\sqrt{2NM_d\omega_{\lambda\mathbf{q}}}} e^{i\mathbf{q}\cdot\mathbf{R}_i} \epsilon_{\lambda\mathbf{q}} (b_{\lambda-\mathbf{q}}^\dagger + b_{\lambda\mathbf{q}}), \quad (4a)$$

$$\mathbf{u}_{[ij]} = \sum_{\lambda\mathbf{q}} \frac{\hbar v_{p,\lambda\mathbf{q}}}{\sqrt{2NM_p\omega_{\lambda\mathbf{q}}}} e^{i\mathbf{q}\cdot\mathbf{R}_{[ij]}} \epsilon_{\lambda\mathbf{q}} (b_{\lambda-\mathbf{q}}^\dagger + b_{\lambda\mathbf{q}}), \quad (4b)$$

with $\mathbf{R}_{[ij]} = (\mathbf{R}_i + \mathbf{R}_j)/2$, M_d the mass of Cu ions, M_p the mass of O ions, $b_{\lambda\mathbf{q}}$ and $b_{\lambda-\mathbf{q}}^\dagger$ annihilation and creation operators of phonons with polarization λ and wave vector $\mathbf{q}$, $\omega_{\lambda\mathbf{q}}$ energies of phonons, $\epsilon_{\lambda\mathbf{q}}$ unit polarization vectors, and N the number of unit cells. The $\mathbf{q}$ dependence of $v_{d,\lambda\mathbf{q}}$ and $v_{p,\lambda\mathbf{q}}$ can play a crucial role; $v_{d,\lambda\mathbf{q}} = 0$ for the breathing modes that bring no changes in adjacent Cu-Cu distances while $v_{p,\lambda\mathbf{q}} \simeq 1$ for such modes.

The electronic part can be well described by the t - J model on a square lattice: $\mathcal{H} = -\sum_{ij\sigma} t_{ij} d_{i\sigma}^\dagger d_{j\sigma} - (J/2) \sum_{\langle ij \rangle} (\mathbf{s}_i \cdot \mathbf{s}_j) + U_\infty \sum_i n_{i\downarrow} n_{i\uparrow}$, with the summation over $\langle ij \rangle$ restricted to nearest neighbors, $\mathbf{s}_i =$

$(1/2) \sum_{\alpha\beta} (\sigma_x^{\alpha\beta}, \sigma_y^{\alpha\beta}, \sigma_z^{\alpha\beta}) d_{i\alpha}^\dagger d_{i\beta}$, with σ_x, σ_y and σ_z the Pauli matrixes, and $n_{i\sigma} = d_{i\sigma}^\dagger d_{i\sigma}$. An infinitely large on-site repulsion, $U_\infty/|t_{ij}| \rightarrow +\infty$, is introduced to exclude any doubly occupied sites. According to Eq. (3), there are two types of electron-phonon interactions. When only longitudinal phonons are considered or when $\epsilon_{\lambda\mathbf{q}} = (q_x, q_y, q_z)/q$ is assumed, they are given by

$$\mathcal{H}_p = iC_p \sum_{\mathbf{q}'\mathbf{q}} \frac{\hbar v_{p,\lambda\mathbf{q}} \bar{\eta}_s(\mathbf{q})}{\sqrt{2NM_p \omega_{\lambda\mathbf{q}}}} \sum_{\Gamma=s,d} \eta_\Gamma(\tfrac{1}{2}\mathbf{q}) \eta_\Gamma(\mathbf{q}') \times \left(b_{\lambda-\mathbf{q}}^\dagger + b_{\lambda\mathbf{q}} \right) [\mathbf{s}(\mathbf{q}' + \tfrac{1}{2}\mathbf{q}) \cdot \mathbf{s}(-\mathbf{q}' + \tfrac{1}{2}\mathbf{q})], \quad (5a)$$

$$\mathcal{H}_d = iC_d \sum_{\mathbf{q}'\mathbf{q}} \frac{\hbar v_{d,\lambda\mathbf{q}}}{\sqrt{2NM_d \omega_{\lambda\mathbf{q}}}} \sum_{\Gamma=s,d} \bar{\eta}_\Gamma(\mathbf{q}) \eta_\Gamma(\mathbf{q}') \times \left(b_{\lambda-\mathbf{q}}^\dagger + b_{\lambda\mathbf{q}} \right) [\mathbf{s}(\mathbf{q}' + \tfrac{1}{2}\mathbf{q}) \cdot \mathbf{s}(-\mathbf{q}' + \tfrac{1}{2}\mathbf{q})], \quad (5b)$$

with $\mathbf{s}(\mathbf{q}) = (1/\sqrt{N}) \sum_{\mathbf{k}\alpha\beta} (1/2) \boldsymbol{\sigma}^{\alpha\beta} d_{(\mathbf{k}+\frac{1}{2}\mathbf{q})\alpha}^\dagger d_{(\mathbf{k}-\frac{1}{2}\mathbf{q})\beta}$,

$$C_p = \frac{4A_d V^4}{(\epsilon_d + U - \epsilon_p)^3} \left[\frac{3}{\epsilon_d + U - \epsilon_p} + \frac{2}{U} \right], \quad (6a)$$

$$C_d = -\frac{2A_p V^4}{(\epsilon_d + U - \epsilon_p)^3} \left[\frac{3}{\epsilon_d + U - \epsilon_p} + \frac{2}{U} \right] + \frac{A_V J}{V}, \quad (6b)$$

$\bar{\eta}_s(\mathbf{q}) = 2[(q_x/q) \sin(q_x a/2) + (q_y/q) \sin(q_y a/2)]$, $\bar{\eta}_d(\mathbf{q}) = 2[(q_x/q) \sin(q_x a/2) - (q_y/q) \sin(q_y a/2)]$, $\eta_s(\mathbf{k}) = \cos(k_x a) + \cos(k_y a)$, and $\eta_d(\mathbf{k}) = \cos(k_x a) - \cos(k_y a)$, with a the lattice constant.

We follow the previous paper [13] to treat the infinitely large U_∞ , where a theory of Kondo lattice is developed. A renormalized single-site approximation (SSA), which includes not only all the single-site terms but also the Fock term $\Delta\Sigma(\mathbf{k})$ due to the superexchange interaction, is reduced to solving the Anderson model. The self-energy of the Anderson model is expanded as $\tilde{\Sigma}_\sigma(i\varepsilon_n) = \tilde{\Sigma}(0) + (1 - \tilde{\phi}_\gamma) i\varepsilon_n + \sum_{\sigma'} (1 - \tilde{\phi}_{\sigma\sigma'}) \Delta\mu_{\sigma'} + \dots$, with $\Delta\mu_\sigma$ a small spin-dependent chemical potential shift. Note that $\tilde{\phi}_\gamma = \tilde{\phi}_{\sigma\sigma}$. The Wilson ratio is defined by $\tilde{W}_s = \tilde{\phi}_s/\tilde{\phi}_\gamma$, with $\tilde{\phi}_s = \tilde{\phi}_{\sigma\sigma} - \tilde{\phi}_{\sigma-\sigma}$. For almost half filling, charge fluctuations are suppressed so that $\tilde{\phi}_c = \tilde{\phi}_{\sigma\sigma} + \tilde{\phi}_{\sigma-\sigma} \ll 1$. For such filling, $\tilde{\phi}_\gamma \gg 1$ so that $\tilde{\phi}_s \simeq 2\tilde{\phi}_\gamma$ or $\tilde{W}_s \simeq 2$. The dispersion relation of quasi-particles is given by $\xi(\mathbf{k}) = (1/\tilde{\phi}_\gamma) [-\sum_j t_{ij} e^{i\mathbf{k} \cdot (\mathbf{R}_i - \mathbf{R}_j)} + \tilde{\Sigma}(0) + \Delta\Sigma(\mathbf{k}) - \mu]$, with μ the chemical potential.

The irreducible polarization function $\pi_s(i\omega_l, \mathbf{q})$ in spin channels is divided into single-site $\tilde{\pi}_s(i\omega_l)$ and multi-site $\Delta\pi_s(i\omega_l, \mathbf{q})$. The spin susceptibility is given by $\chi_s(i\omega_l, \mathbf{q}) = 2\pi_s(i\omega_l, \mathbf{q}) / \{1 - [\frac{1}{2}J(\mathbf{q}) + U_\infty] \pi_s(i\omega_l, \mathbf{q})\}$, with $J(\mathbf{q}) = 2J\eta_s(\mathbf{q})$. In Kondo lattices, local spin fluctuations at different sites interact with each other by an exchange interaction. Following this physical picture, we define an exchange interaction $I_s(i\omega_l, \mathbf{q})$ by

$$\chi_s(i\omega_l, \mathbf{q}) = \tilde{\chi}_s(i\omega_l) / [1 - \frac{1}{4} I_s(i\omega_l, \mathbf{q}) \tilde{\chi}_s(i\omega_l)], \quad (7)$$

with $\tilde{\chi}_s(i\omega_l) = 2\tilde{\pi}_s(i\omega_l) / [1 - U_\infty \tilde{\pi}_s(i\omega_l)]$ the susceptibility for the Anderson model. Then, $I_s(i\omega_l, \mathbf{q}) = J(\mathbf{q}) + 2U_\infty^2 \Delta\pi_s(i\omega_l, \mathbf{q})$. When the Ward relation [18] is made

use of, the irreducible single-site three-point vertex function in spin channels, $\tilde{\lambda}_s(i\varepsilon_n, i\varepsilon_n + i\omega_l; i\omega_l)$, is given by

$$\lim_{U_\infty \rightarrow +\infty} U_\infty \tilde{\lambda}_s(i\varepsilon_n, i\varepsilon_n + i\omega_l; i\omega_l) = 2\tilde{\phi}_s / \tilde{\chi}_s(i\omega_l), \quad (8)$$

for $|\varepsilon_n| \rightarrow +0$ and $|\omega_l| \rightarrow +0$. We approximately use Eq. (8) for $|\varepsilon_n| \lesssim k_B T_K$ and $|\omega_l| \lesssim k_B T_K$, with T_K the Kondo temperature defined by $k_B T_K = [1/\tilde{\chi}_s(0)]_{T \rightarrow 0}$. The main term of $2U_\infty^2 \Delta\pi_s(i\omega_l, \mathbf{q})$ is an exchange interaction arising from the virtual exchange of pair excitations of quasi-particles, which is less effective than $J(\mathbf{q})$. The so called spin-fluctuation mediated interaction, whose single-site term should be subtracted because it is considered in SSA, is given by $\frac{1}{4} [2\tilde{\phi}_s / \tilde{\chi}_s(i\omega_l)]^2 [\chi_s(i\omega_l, \mathbf{q}) - \tilde{\chi}_s(i\omega_l)]$. It is simply given by $\tilde{\phi}_s^2 \frac{1}{4} I_s^*(i\omega_l, \mathbf{q})$, with

$$\frac{1}{4} I_s^*(i\omega_l, \mathbf{q}) = \frac{\frac{1}{4} I_s(i\omega_l, \mathbf{q})}{1 - \frac{1}{4} I_s(i\omega_l, \mathbf{q}) \tilde{\chi}_s(i\omega_l)}. \quad (9)$$

Because of these equations, we call $I_s(i\omega_l, \mathbf{q})$ a bare exchange interaction, $I_s^*(i\omega_l, \mathbf{q})$ an enhanced one, and $\tilde{\phi}_s$ an effective three-point vertex function in spin channels.

The enhanced one is expanded as $I_s^*(i\omega_l, \mathbf{q}) = I_0^* + 2I_1^* \eta_s(\mathbf{q}) + \dots$. The nearest-neighbor I_1^* is mainly responsible for the development of not only SC but also charge bond-order (CBO) fluctuations [19]. Because contributions from $|\omega_l| \lesssim k_B T_K$ are the most effective, we ignore its energy dependence. An effective SC susceptibility, which is multiplied by $\tilde{\phi}_s^2$, is calculated in the ladder approximation with respect to I_1^* :

$$\chi_{\Gamma=d}^{(\text{SC})}(i\omega_l, \mathbf{q}) = \frac{2\tilde{W}_s^2 \pi_d^{(\text{SC})}(i\omega_l, \mathbf{q})}{1 + \frac{3}{4} I_1^* \tilde{W}_s^2 \pi_d^{(\text{SC})}(i\omega_l, \mathbf{q})}, \quad (10)$$

for $\Gamma = d$ wave, with

$$\pi_\Gamma^{(\text{SC})}(i\omega_l, \mathbf{q}) = \frac{k_B T}{N} \sum_{\mathbf{n}\mathbf{k}} \eta_\Gamma^2(\mathbf{k}) \frac{1}{i\varepsilon_n - \xi(\mathbf{k} + \frac{1}{2}\mathbf{q})} \times \frac{1}{-i\varepsilon_n - i\omega_l - \xi(-\mathbf{k} + \frac{1}{2}\mathbf{q})}, \quad (11)$$

Only d -wave SC fluctuation are considered in this Letter. An effective CBO susceptibility is similarly given by

$$\chi_\Gamma^{(\text{CBO})}(i\omega_l, \mathbf{q}) = \frac{2\tilde{W}_s^2 \pi_\Gamma^{(\text{CBO})}(i\omega_l, \mathbf{q})}{1 + \frac{3}{4} I_1^* \tilde{W}_s^2 \pi_\Gamma^{(\text{CBO})}(i\omega_l, \mathbf{q})}, \quad (12)$$

for $\Gamma = s, p$ and d waves, with

$$\pi_\Gamma^{(\text{CBO})}(i\omega_l, \mathbf{q}) = -\frac{k_B T}{N} \sum_{\mathbf{n}\mathbf{k}} \eta_\Gamma^2(\mathbf{k}) \frac{1}{i\varepsilon_n - \xi(\mathbf{k} - \frac{1}{2}\mathbf{q})} \times \frac{1}{i\varepsilon_n + i\omega_l - \xi(\mathbf{k} + \frac{1}{2}\mathbf{q})}. \quad (13)$$

The form factors of p waves are defined by $\eta_x(\mathbf{k}) = \sqrt{2} \sin(k_x a)$ and $\eta_y(\mathbf{k}) = \sqrt{2} \sin(k_y a)$.

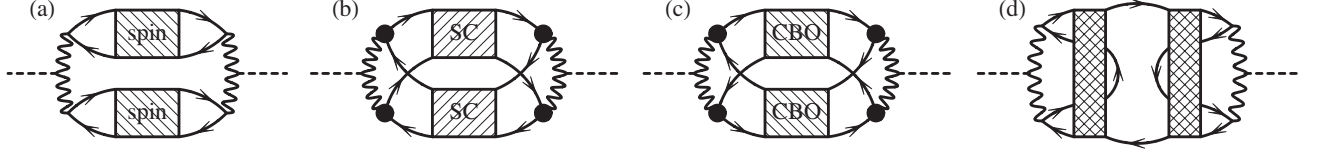


FIG. 1: Four processes contributing to the renormalization of phonons. A solid line stands for an electron, a broken line for a phonon, a wavy line for the superexchange interaction J , and a solid circle for the effective vertex function $\tilde{\phi}_s$.

A renormalized Green function for phonons is given by $D_\lambda(i\omega_l, \mathbf{q}) = 2\omega_{\lambda\mathbf{q}} / [(i\omega_l)^2 - \omega_{\mathbf{q}\lambda}^2 + 2\omega_{\lambda\mathbf{q}}\Delta\omega_\lambda(i\omega_l, \mathbf{q})]$, with $\Delta\omega_\lambda(i\omega_l, \mathbf{q}) = -(\hbar^2/2M_p\omega_{\lambda\mathbf{q}}) S(i\omega_l, \mathbf{q})$. Because phonons are renormalized by AFS, SC and CBO fluctuations as well as pair excitations of quasi-particles in charge channels or charge density fluctuations, we consider four processes shown in Fig. 1. When only the part of $\Gamma = s$ in Eq. (5) is considered, it follows that $S = S_s + S_{\text{SC}} + S_{\text{CBO}} + S_c$, with

$$S_s(i\omega_l, \mathbf{q}) = \frac{3}{4^2} Y_\lambda^2(\mathbf{q}) \frac{k_B T}{N} \sum_{\nu' \mathbf{q}'} \eta_s^2(\mathbf{q}') \chi_s(i\omega_l + i\omega_{\nu'}, \mathbf{q}' + \frac{1}{2}\mathbf{q}) \chi_s(i\omega_l - i\omega_{\nu'}, -\mathbf{q}' + \frac{1}{2}\mathbf{q}), \quad (14a)$$

$$S_{\text{SC}}(i\omega_l, \mathbf{q}) = \frac{3^2}{4^3} Y_\lambda^2(\mathbf{q}) \frac{k_B T}{N} \sum_{\nu' \mathbf{q}'} \chi_d^{\text{SC}}(i\omega_l + i\omega_{\nu'}, \mathbf{q}' + \frac{1}{2}\mathbf{q}) \chi_d^{\text{SC}}(i\omega_l - i\omega_{\nu'}, -\mathbf{q}' + \frac{1}{2}\mathbf{q}), \quad (14b)$$

$$S_{\text{CBO}}(i\omega_l, \mathbf{q}) = \frac{3^2}{4^3} Y_\lambda^2(\mathbf{q}) \sum_{\Gamma} \frac{k_B T}{N} \sum_{\nu' \mathbf{q}'} \chi_\Gamma^{\text{CBO}}(i\omega_l + i\omega_{\nu'}, \mathbf{q}' + \frac{1}{2}\mathbf{q}) \chi_\Gamma^{\text{CBO}}(i\omega_l - i\omega_{\nu'}, -\mathbf{q}' + \frac{1}{2}\mathbf{q}), \quad (14c)$$

$$S_c(i\omega_l, \mathbf{q}) = -\frac{3^2}{4^2} \tilde{W}_s^4 \frac{k_B T}{N} \sum_{n\sigma \mathbf{k}} Z^2(i\varepsilon_n, i\omega_l; \mathbf{k}, \mathbf{q}) \frac{1}{i\varepsilon_n - \xi(\mathbf{k})} \frac{1}{i\varepsilon_n + i\omega_l - \xi(\mathbf{k} + \mathbf{q})}, \quad (14d)$$

with $Y_\lambda(\mathbf{q}) = \bar{\eta}_s(\mathbf{q}) [C_p v_{p,\lambda\mathbf{q}} \eta_s(\frac{1}{2}\mathbf{q}) + C_d v_{d,\lambda\mathbf{q}} \sqrt{M_p/M_d}]$. Here, $Z(i\varepsilon_n, i\omega_l; \mathbf{k}, \mathbf{q})$ is a vertex function in the charge-density channel. It is also enhanced by AFS, SC and CBO fluctuations; $Z = Z_s + Z_{\text{SC}} + Z_{\text{CBO}} + \dots$, with

$$Z_s(i\varepsilon_n, i\omega_l; \mathbf{k}, \mathbf{q}) = Y_\lambda(\mathbf{q}) \frac{k_B T}{N} \sum_{\nu' \mathbf{q}'} \eta_s(\mathbf{q}') \frac{K_s(i\omega_{\nu'} + i\frac{1}{2}\omega_l, \mathbf{q}' + \frac{1}{2}\mathbf{q}) K_s(-i\omega_{\nu'} + i\frac{1}{2}\omega_l, -\mathbf{q}' + \frac{1}{2}\mathbf{q})}{i\varepsilon_n + i\omega_{\nu'} + \frac{1}{2}\omega_l - \xi(\mathbf{k} + \mathbf{q}' + \frac{1}{2}\mathbf{q})}, \quad (15a)$$

$$Z_{\text{SC}}(i\varepsilon_n, i\omega_l; \mathbf{k}, \mathbf{q}) = \frac{1}{2} Y_\lambda(\mathbf{q}) \frac{k_B T}{N} \sum_{\nu' \mathbf{q}'} \eta_d(\mathbf{k} - \frac{1}{2}\mathbf{q}' + \frac{1}{4}\mathbf{q}) \eta_d(\mathbf{k} - \frac{1}{2}\mathbf{q}' + \frac{3}{4}\mathbf{q}) \times \frac{K_d^{\text{SC}}(i\omega_{\nu'} - i\frac{1}{2}\omega_l, \mathbf{q}' - \frac{1}{2}\mathbf{q}) K_d^{\text{SC}}(i\omega_{\nu'} + i\frac{1}{2}\omega_l, \mathbf{q}' + \frac{1}{2}\mathbf{q})}{-i\varepsilon_n + i\omega_{\nu'} - i\frac{1}{2}\omega_l - \xi(-\mathbf{k} + \mathbf{q}' - \frac{1}{2}\mathbf{q})}, \quad (15b)$$

$$Z_{\text{CBO}}(i\varepsilon_n, i\omega_l; \mathbf{k}, \mathbf{q}) = -\frac{1}{2} Y_\lambda(\mathbf{q}) \frac{k_B T}{N} \sum_{\nu' \mathbf{q}'} \sum_{\Gamma} \eta_\Gamma(\mathbf{k} + \frac{1}{2}\mathbf{q}' + \frac{1}{2}\mathbf{q}) \eta_\Gamma(\mathbf{k} + \frac{1}{2}\mathbf{q}' + \frac{3}{4}\mathbf{q}) \times \frac{K_\Gamma^{\text{CBO}}(i\omega_{\nu'} + i\frac{1}{2}\omega_l, \mathbf{q}' + \frac{1}{2}\mathbf{q}) K_\Gamma^{\text{CBO}}(-i\omega_{\nu'} + i\frac{1}{2}\omega_l, -\mathbf{q}' + \frac{1}{2}\mathbf{q})}{i\varepsilon_n + i\omega_{\nu'} + i\frac{1}{2}\omega_l - \xi(\mathbf{k} + \mathbf{q}' + \frac{1}{2}\mathbf{q})}, \quad (15c)$$

with

$$K_s(i\omega_l, \mathbf{q}) = \frac{1}{1 - \frac{1}{4} I(i\omega_l, \mathbf{q}) \tilde{\chi}_s(i\omega_l)}, \quad K_d^{\text{SC}}(i\omega_l, \mathbf{q}) = \frac{-\frac{3}{4} I_1^* \pi_d^{\text{SC}}(i\omega_l, \mathbf{q})}{1 + \frac{3}{4} I_1^* \pi_d^{\text{SC}}(i\omega_l, \mathbf{q})}, \quad K_\Gamma^{\text{CBO}}(i\omega_l, \mathbf{q}) = \frac{-\frac{3}{4} I_1^* \pi_\Gamma^{\text{CBO}}(i\omega_l, \mathbf{q})}{1 + \frac{3}{4} I_1^* \pi_\Gamma^{\text{CBO}}(i\omega_l, \mathbf{q})}. \quad (16)$$

No softening occurs for $\mathbf{q} = 0$ because $\bar{\eta}_s(\mathbf{q} \rightarrow 0) \propto |\mathbf{q}|$. When $\mathbf{q}$ goes from Γ point to the zone boundary, the softening must increase first. However, it is unlikely that the softening is the largest at the zone boundary. For example, consider the breathing mode at X point, $\mathbf{q}_X = (\pm\pi/a, 0)$. Because $v_{d,\lambda\mathbf{q}_X} = 0$, the electron-phonon interaction described by Eq. (5b) vanishes. For $\mathbf{q} \neq \mathbf{q}_X$, $v_{d,\lambda\mathbf{q}}$ is nonzero. This implies that the softening may not be the largest at X point along Γ - X line. In actual, several experimental data show that the softening is the largest for $\mathbf{q}$ a little different from $\mathbf{q}_X$ [3, 6].

Because a low-energy scale is $k_B T_K$, we put

$$S(i\omega_l, \mathbf{q}) \simeq s/k_B T_K, \quad (17) \quad \text{with } s = O(1) \text{ a dimensionless constant. It follows that}$$

$$\Delta\omega_\lambda(\omega_{\lambda\mathbf{q}_X}, \mathbf{q}_X) \simeq -15 s c_p^2 \text{ meV}, \quad (18)$$

for

$$C_p \simeq c_p \text{ eV}/\text{\AA}, \quad \omega_{\lambda\mathbf{q}_X} = 0.1 \text{ eV}, \quad k_B T_K = 0.1 \text{ eV}, \quad (19)$$

with $c_p = O(1)$ a dimensionless constant. When we take

$$V \simeq 1.6 \text{ eV}, \quad \epsilon_{3d} - \epsilon_{2p} \simeq -1 \text{ eV}, \quad U \simeq 5 \text{ eV}, \quad (20)$$

following the previous paper [17], it follows that $c_p = (0.5-1)$ for $A_d = (1-2) \text{ eV}/\text{\AA}$. If $sc_p^2 \simeq 1$, the observed softening as large as [2, 3, 4, 5, 6]

$$\Delta\omega_\lambda(\omega_{\lambda\mathbf{q}_X}, \mathbf{q}_X) \simeq -10 \text{ meV}, \quad (21)$$

can be explained. It should be examined whether sc_p^2 is actually as large as 1.

A process corresponding to Fig. 1(d) renormalizes quasi-particles. The self-energy correction is given by

$$\begin{aligned} \frac{1}{\tilde{\phi}_\gamma} \Delta\Sigma(i\varepsilon_n, \mathbf{k}) = & -\frac{k_B T}{N} \sum_{\lambda\mathbf{l}\mathbf{q}} g_\lambda^2(i\varepsilon_n, i\omega_l; \mathbf{k}, \mathbf{q}) D_\lambda(i\omega_l, \mathbf{q}) \\ & \times \frac{1}{i\varepsilon_n + i\omega_l - \xi(\mathbf{k} + \mathbf{q})}, \end{aligned} \quad (22)$$

with

$$g_\lambda(i\varepsilon_n, i\omega_l; \mathbf{k}, \mathbf{q}) = C_p \frac{\hbar}{\sqrt{2M_p\omega_{\lambda\mathbf{q}}}} \frac{3}{4} \tilde{W}_s^2 Z(i\varepsilon_n, i\omega_l; \mathbf{k}, \mathbf{q}). \quad (23)$$

It is likely that the contribution of Fig. 1(d) dominate those of the other three, Figs. 1(a)–(c). In such a case,

$$g_\lambda(i\varepsilon_n, i\omega_l; \mathbf{k}, \mathbf{q}) \simeq \sqrt{k_B T_K |\Delta\omega_\lambda(\omega_{\lambda\mathbf{q}_X}, \mathbf{q}_X)|}. \quad (24)$$

When the experimental value (21) is used, we obtain

$$g_\lambda(i\varepsilon_n, i\omega_l; \mathbf{k}, \mathbf{q}) \simeq 30 \text{ meV}. \quad (25)$$

This is large enough for optical phonons to cause kinks in the dispersion relation of quasi-particles. Two types of kinks are observed [10]. The renormalization by phonons can explain one type of kinks observed in both normal and SC phases. However, it cannot explain the other type of kinks observed only in SC phases.

The phonon-mediated pair interaction is given by $g_\lambda^2(0, 0; \mathbf{k}, \mathbf{q}) D_\lambda(0, \mathbf{q})$ or $-2g_\lambda^2(0, 0; \mathbf{k}, \mathbf{q})/\omega_{\lambda\mathbf{q}}$. The softening of phonons is the largest for $\mathbf{q} \simeq \mathbf{q}_X$ along Γ -X line. This implies that the pair interaction by phonons is attractive between nearest neighbors. The nearest-neighbor part of $-2g_\lambda^2(0, 0; \mathbf{k}, \mathbf{q})/\omega_{\lambda\mathbf{q}}$ should be included in $\frac{3}{4}I_1^*$. According to the argument in this Letter, it follows that

$$-2g_\lambda^2(0, 0; \mathbf{k}, \mathbf{q}_X)/\omega_{\lambda\mathbf{q}_X} \simeq -20 \text{ meV}. \quad (26)$$

The phonon-mediated interaction cannot be ignored in cuprate-oxide superconductors. However, it is smaller

than $\frac{3}{4}|I_1^*| \simeq 100 \text{ meV}$. The main Cooper-pair interaction must be the superexchange interaction.

There are two other types of electron-phonon interactions. Note that $\tilde{\phi}_c$ and $1/\tilde{\phi}_\gamma$ are small parameters in the vicinity of the Mott-Hubbard transition. The conventional one arising from the modulation of $3d$ -electron levels, which can directly couples with charge fluctuations, gives renormalization effects higher order in $\tilde{\phi}_c$ and $1/\tilde{\phi}_\gamma$. The interaction arising from the modulation of t_{ij} gives renormalization effects higher order in $1/\tilde{\phi}_\gamma$. Then, we ignore both of them. On the other hand, what are considered in this Letter are of the order of $(\tilde{\phi}_c)^0(1/\tilde{\phi}_\gamma)^0$.

In conclusion, we propose the electron-phonon interaction arising from the modulation of the superexchange interaction by phonons, which is only relevant for strongly correlated electron liquids in the vicinity of the Mott-Hubbard transition. Its novel property is that it can be enhanced by spin, superconducting, and charge bond-order fluctuations as well as charge density fluctuations. A phenomenological argument where parameters are determined from the observed softening of phonons implies that the enhanced electron-phonon interaction is also responsible for kinks in the dispersion relation of quasi-particles in cuprate-oxide high- T_c superconductors. However, it can never be the main Cooper-pair interaction. The main one must be the superexchange interaction.

This work is supported by a Grant-in-Aid for Scientific Research (C) No. 13640342 from the Japan Society for the promotion of Science.

* Electronic address: fohkawa@phys.sci.hokudai.ac.jp

- [1] J.G. Bednrotz and K.A. Müller, Z. Phys. B **64**, 189 (1986)
- [2] R.J. McQueeney, et al., Phys. Rev. Lett. **82**, 628 (1999).
- [3] L.Pintschovius and M. Braden, Phys. Rev. B **60**, R15039 (1999).
- [4] R.J. McQueeney, et al., Phys. Rev. Lett. **87** 077001 (2001).
- [5] L. Pintschovius, et al., Phys. Rev. B **64**, 094510 (2001).
- [6] M. Braden et al., Physica C **378-381**, 89 (2002).
- [7] J.C. Campuzano, et al., Phys. Rev. Lett. **83**, 3709 (1999).
- [8] A. Lanzara, et al., Nature **412**, 510 (2001).
- [9] P.D. Johnson et al., Phys. Rev. Lett. **87**, 177007 (2001).
- [10] T. Sato, et al., Phys. Rev. Lett. **91**, 157003 (2003).
- [11] F.J. Ohkawa, Jpn. J. Appl. Phys. **26**, L652 (1987).
- [12] F.J. Ohkawa, J. Phys. Soc. Jpn. **56**, 2267 (1987).
- [13] F.J. Ohkawa, submitted to Phys. Rev. B (#BE9029); cond-matt/0305422.
- [14] F.J. Ohkawa, J. Phys. Soc. Jpn. **58**, 4156 (1989).
- [15] M. C. Gutzwiller, Phys. Rev. Lett. **10**, 159 (1963).
- [16] J. Hubbard, Proc. Roy. Soc. A **276**, 283 (1963).
- [17] F.J. Ohkawa, Phys. Rev. B **59**, 8930 (1999).
- [18] J. C. Ward, Phys. Rev. **68**, 182 (1950).
- [19] The order parameter of CBO is $\sum_\sigma \langle a_{i\sigma}^\dagger a_{j\sigma} \rangle$ with $i \neq j$; bond order should not be called anisotropic density wave.